



Material No.: Code: **1.2379 X153CrMoV12**

DE - Brand: **CPPU**

Chemical composition:
(Typical analysis in %)

C	Cr	Mo	V				
1,55	12,00	0,80	0,90				

Steel properties:

Ledeburitic 12% chrome steel, very high resistance against abrasive and adhesive wear due to a high volume of hard carbides in the steel matrix, good toughness, very good dimensional stability, high compressive strength, very good base material for PVD/CVD coating as well as nitriding due to its secondary hardening properties. Similar to AISI D2.

Applications:

Cutting, punching, stamping tools, shear blades, thread rolling dies, cold extrusion dies, drawing and bending tools, flanging and straightening rolls, fine cutting tools, deep drawing tools, plastic moulds for abrasive polymers.

Condition of delivery:

Soft annealed to max. 255 HB

Physical properties:

Thermal expansion coefficient	$\left[\frac{10^{-6} \cdot \text{m}}{\text{m} \cdot \text{K}} \right]$	$\frac{20-100^{\circ}\text{C}}{10,5}$	$\frac{20-200^{\circ}\text{C}}{11,5}$	$\frac{20-300^{\circ}\text{C}}{11,9}$	$\frac{20-400^{\circ}\text{C}}{13,0}$
Thermal conductivity	$\left[\frac{\text{W}}{\text{m} \cdot \text{K}} \right]$	$\frac{20^{\circ}\text{C}}{16,7}$	$\frac{350^{\circ}\text{C}}{20,5}$	$\frac{700^{\circ}\text{C}}{24,2}$	


Heat treatment:

	Temperature	Cooling	Hardness
Soft annealing	820 - 850°C	furnace	max. 255 HB


	Temperature	Cooling	
Stress relief annealing	600 - 650°C	furnace	

	Temperature	Cooling	Tempering
Hardening	1000 - 1030°C	oil, pressure gas (N ₂), air or hot bath 500 - 550°C	see tempering diagram ① usually < 300°C
	1040 - 1080°C	oil, pressure gas (N ₂), air or hot bath 500 - 550°C	see tempering diagram ② usually > 480°C


(1.2379) Thermal Cycle Diagram

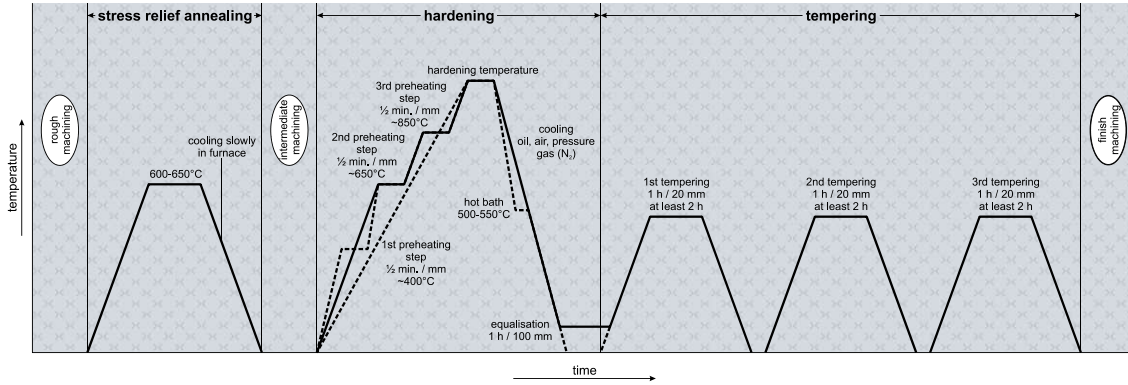

Continuous Cooling Transformation Diagram (CCT)

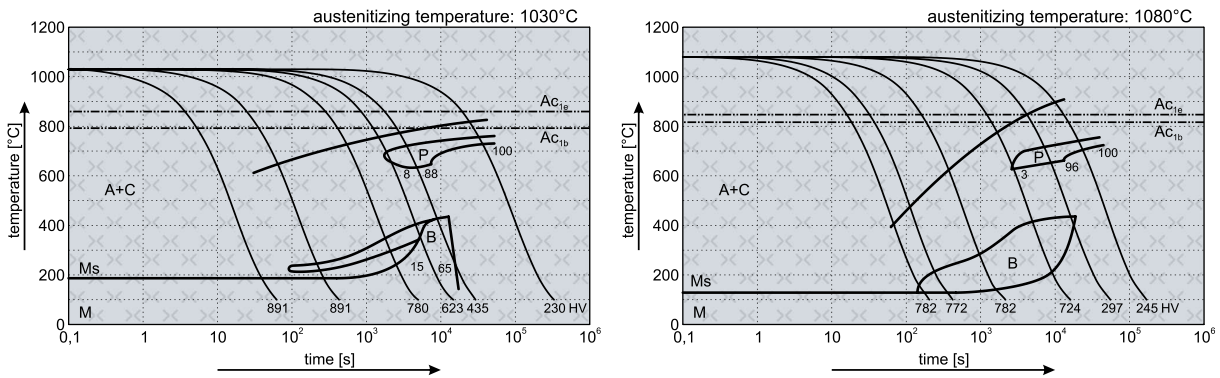

Tempering Diagram

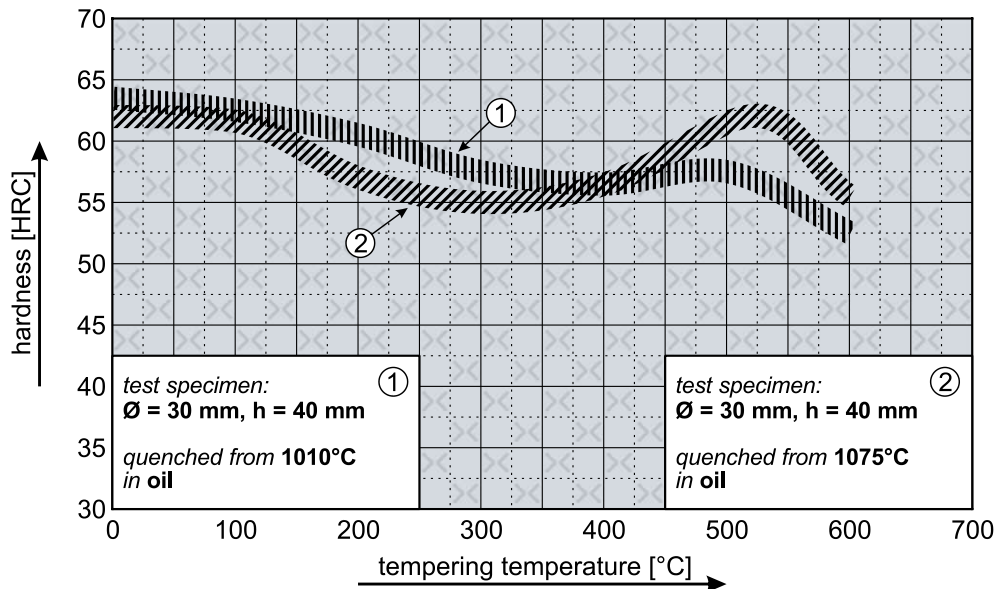

Remarks: All technical information is for reference only.